



**UNIVERSITI PUTRA MALAYSIA**

**EFFECT OF PbO ON THE ELASTIC PROPERTIES OF  
BORATE AND PHOSPHATE GLASS SYSTEM**

**AZMAN B. KASIM**

**FSAS 2000 31**

**EFFECT OF PbO ON THE ELASTIC PROPERTIES  
OF BORATE AND PHOSPHATE GLASS SYSTEM**

**By**

**AZMAN B. KASIM**

**Thesis Submitted in Fulfilment of the Requirements for the Degree of  
Master of Science in the Faculty of Science & Environmental Studies  
Universiti Putra Malaysia**

**July 2000**



## DEDICATIONS

*To...*

*My wife, Nazrah*

*My Dad, Hj. Kasim*

*My Mum, Hj. Jamilah*

*My Brother, Azrin Kasim*

*My Sister, Noor Azah Kasim*

*... Thanks for your support  
And endless love...*

Abstract of the thesis presented to the Senate Of Universiti Putra Malaysia  
in fulfilment of the requirements for the degree of Master of Science

**EFFECT OF PbO ON THE ELASTIC PROPERTIES  
OF BORATE AND PHOSPHATE GLASS SYSTEM**

By

**AZMAN BIN KASIM**

**July 2000**

**Chairman: Assoc. Prof. Sidek Hj. Ab. Aziz, Ph.D**

**Faculty: Science and Environmental Studies**

The effect of PbO on the elastic properties phosphate of glass and borate glass system has been studied. A series of lead borate glasses  $[\text{PbO}_x \cdot (\text{B}_2\text{O}_3)_{x-1}]$  ( $0.30 \leq X \leq 0.45$ ) and lead phosphate glasses  $[\text{PbO}_x \cdot (\text{P}_2\text{O}_5)_{x-1}]$  ( $0.10 \leq X \leq 0.60$ ) were successfully synthesized. By using ultrasonic measurement system, the velocities of the propagated waves attained could be used to estimate the elastic properties of glass. In this studies, the velocities of propagated waves in lead borate and lead phosphate are found to decrease with the mole fraction of PbO. Meanwhile, the addition of PbO increases the density of glasses. It shows that lead borate and lead phosphate glasses become more rigid but undergone a weakening structure. Hence, an addition of PbO will affect the elastic properties of glass. From the

experimental results the elastic modulus  $C_{11}$  and  $C_{44}$ , Young's modulus ( $E$ ); bulk modulus ( $B$ ) and Poisson ratio ( $\sigma$ ) are also found to vary with the mole fraction of PbO. The Debye temperatures, which describe the thermal behaviour for isotropic materials such as glass also show a decreasing trend with the mole fraction of PbO. It seems that an addition of PbO into the borate and phosphate glass systems changes the coordination of the glass structure and weakens the glass network by the increase of non-bridging oxygens (NBOs).

From the structural aspect, the lead borate glass consists of  $\text{BO}_3$  and  $\text{BO}_4$  units, which change markedly with the PbO content. At low PbO concentration ( $x \leq 0.15$ ), lead is assumed to assist in the formation of  $\text{BO}_4$  tetrahedral. Whereas, for high PbO content ( $x > 0.15$ ), some of lead act to form  $\text{PbO}_4$  pyramid. Meanwhile, for lead phosphate glasses, since the basic structure is  $\text{PbO}_4$  tetrahedral, hence an increment of PbO content tend to reduce the number of cross-linking P-O-P bonds between pairs of tetrahedral and increase the number of chains of  $\text{PO}_4$  tetrahedral.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk memperolehi ijazah Master Sains.

## **KESAN PbO TERHADAP SIFAT KENYAL KACA BORAT DAN KACA FOSFAT**

Oleh

**AZMAN BIN KASIM**

**Julai 2000**

**Pengerusi : Prof. Madya Sidek Hj. Ab. Aziz, Ph.D**

**Fakulti : Sains dan Pengajian Alam Sekitar.**

Kesan PbO terhadap sifat-sifat kenyal kaca borat dan fosfat telah dikaji. Satu siri kaca borat  $[\text{PbO}_x \cdot (\text{B}_2\text{O}_3)_{x-1}]$  ( $0.30 \leq X \leq 0.45$ ) dan kaca fosfat  $[\text{PbO}_x \cdot (\text{P}_2\text{O}_5)_{x-1}]$  ( $0.10 \leq X \leq 0.60$ ) telah pun disediakan. Dengan menggunakan sistem pengukuran ultrasonik, halaju perambatan gelombang yang diperolehi telah digunakan untuk menganggar sifat kenyal bagi kaca. Dalam kajian ini didapati halaju gelombang yang merambat dalam kaca borat dan fosfat berkurangan terhadap pertambahan PbO. Pertambahan PbO juga turut meningkatkan ketumpatan kaca-kaca tersebut. Ini menunjukkan kaca plumbum borat dan plumbum fosfat menjadi lebih keras tetapi mempunyai struktur yang lemah. Pertambahan PbO telah memberi kesan terhadap sifat kenyal kaca. Daripada hasil ujikaji didapati modulus kenyal  $C_{11}$  dan  $C_{44}$ , modulus Young (E), modulus pukal (B) dan nisbah

Poisson ( $\sigma$ ) turut berubah terhadap plumbum oksida. Suhu Debye yang menerangkan tentang ciri-ciri terma bagi bahan isotropik seperti kaca juga menunjukkan penurunan terhadap kandungan PbO. Maka, pertambahan ion plumbum ke dalam sistem kaca borat dan kaca fosfat telah mengubah koordinasi struktur kaca dan melemahkan rangkaian kaca disebabkan oleh pertambahan bilangan oksigen bebas (NBOs).

Dari aspek struktur, kaca plumbum borat yang mengandungi unit  $\text{BO}_3$  dan  $\text{BO}_4$  turut mengalami perubahan terhadap kandungan PbO. Bagi kandungan PbO rendah ( $x < 0.15$ ), plumbum dikatakan membantu pembentukan  $\text{BO}_4$  tetrahedra. Manakala, untuk kandungan PbO tinggi ( $x > 0.15$ ), sebahagian daripada plumbum bertindak membentuk piramid  $\text{PbO}_4$ . Bagi kaca plumbum fosfat yang mempunyai struktur asas  $\text{PO}_4$  tetrahedra, pertambahan PbO telah mengurangkan hubungan silang ikatan P-O-P antara pasangan tetrahedra dan meningkatkan sejumlah bilangan rangkaian  $\text{PO}_4$  tetrahedra.

## ACKNOWLEDGMENTS

In the name of Allah, the Most Gracious and Most Merciful. Praise be upon Him for enabling me to complete this project.

First and foremost, I would like to extend my heartfelt thanks to my supervisor Assoc. Prof. Dr. Sidek Ab. Aziz for his constant monitoring, enthusiasm, encouragement and support throughout the course of the project and during the writing of this thesis. With his patience and guidance, at last I have completed my thesis. Working with Dr. Sidek has provided me a vast understanding on ultrasonic techniques and theoretical experiences.

Special thanks are dedicated to members of my co-supervisors, Assoc. Prof. Dr. Chow Sai Pew, Prof. Dr. Halim Shaari and Assoc. Prof. Dr. Senin Hassan for their wholehearted support especially for the glassy knowledge and many helpful discussions. To my past and present colleagues at Physics Dept., UPM, I wish to thank them for their moral support.

Also, I would like to express my gratitude and love to my wife, NAZRAH JUMHURI, to my parents, HJ. KASIM ABD. SAMAD and HJH. JAMILAH BT. ABD. RAHMAN, my brother and sister for their endless-continued love, understanding and inspiration. I also gratefully acknowledge



the following people who have unselfishly given their assistance, En. Radzi and En. Zainuddin `Din Ferrite'. Also a special thanks to UPM for giving me a great opportunity to use the material and research facilities.

Finally, I wish them every success in this world and hereafter under the guidance and in the path of Allah s.w.t. I love you all, thank you.


I certify that an Examination Committee met on 26 July 2000 to conduct the final examination of Azman b. Kasim on his Master of Science thesis entitled "Effect of PbO on the Elastic Properties of Lead Borate and Lead Phosphate Glass System" in accordance with Universiti Pertanian Malaysia (Higher Degree) Act 1980 and Universiti Pertanian Malaysia (Higher Degree) Regulations 1981. The committee recommends that candidate be awarded the relevant degree. Members of the Examination Committee are as follows:

HJ. JAMIL B. SURADI, Ph.D  
Physics Department,  
Faculty of Science and Environmental Studies  
Universiti Putra Malaysia  
(Chairman)

SIDEK B. AB. AZIZ, Ph.D  
Associate Professor  
Physics Department  
Faculty of Science and Environmental Studies  
Universiti Putra Malaysia  
(Member)

CHOW SAI PEW, Ph.D  
Associate Professor  
Physics Department  
Faculty of Science and Environmental Studies  
Universiti Putra Malaysia  
(Member)

AB. HALIM B. SHAARI, Ph.D  
Professor/Deputy Dean  
Faculty of Science and Environmental Studies  
Universiti Putra Malaysia  
(Member)

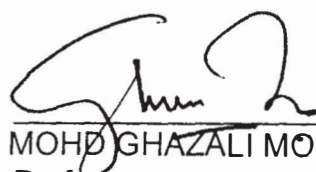

MOHD GHAZALI MOHAYIDIN, Ph.D  
Professor  
Deputy Dean of Graduate School  
Universiti Putra Malaysia

11 SEP 2000

This thesis was submitted to the Senate of Universiti Putra Malaysia and was accepted as fulfilment of the requirements for the degree of Master of Science.




---

KAMIS AWANG, Ph.D  
Associate Professor,  
Dean of Graduate School  
Universiti Putra Malaysia

Date: **11 NOV 2000**

## DECLARATION

I hereby declare that the thesis is based on my original work except for quotations and citations, which have been duly acknowledged. I also declare that it has not been previously or concurrently submitted for any other degree at Universiti Putra Malaysia or other institutions.



---

( AZMAN B. KASIM)

Date: 1. 9. 2000

## TABLE OF CONTENTS

	Page
DEDICATION.....	ii
ABSTRACT.....	iii
ABSTRAK.....	v
ACKNOWLEDGEMENTS.....	vii
APPROVAL SHEETS.....	ix
DECLARATION FORM.....	xi
LIST OF TABLES.....	xv
LIST OF FIGURES.....	xvi
LIST OF SYMBOLS AND ABBREVIATIONS.....	xix
 <b>CHAPTER</b>	
<b>I</b> <b>INTRODUCTION.....</b>	<b>1</b>
Glass History.....	1
Research Background.....	3
Objective of Study.....	4
Chapter Organisation.....	5
 <b>II</b> <b>GLASS TECHNOLOGY.....</b>	<b>7</b>
Introduction.....	7
Uses of Glass.....	8
Glass Families of Interest.....	9
Vitreous Silica.....	9
Soda-lime glass.....	10
Borosilicate glass.....	10
Alkali Silicate glass.....	11
Lead Silicate glass.....	11
Aluminosilicate glass.....	12
Other Silica-Based oxide glass.....	12
Other Non-Silica-Based oxide glass.....	12
Chalcogenide and Chalcogen halide oxide glass.....	13
Literature Review.....	13
Summary.....	16
 <b>III</b> <b>THEORY OF GLASS.....</b>	<b>18</b>
Introduction.....	18
Glass Definition.....	18
Structural Consideration of the glass.....	19
Network Formers.....	20
Network Modifier.....	21
Intermediate Modifier.....	22
Doping Salt.....	23

CHAPTER		Page
	Random Network Theory.....	23
	Molecular Structure.....	25
	Borate Glasses.....	25
	Phosphate Glasses.....	26
	Glass Transformation.....	28
	Glass Formation Range.....	29
	Composition-Structure-Property Relationship.....	32
	Summary.....	34
<b>IV</b>	<b>THEORY OF ELASTICITY.....</b>	<b>35</b>
	Introduction.....	35
	The Elastic Theory of Solid.....	36
	Elastic Properties of Glass.....	39
	The Stress-Strain Relationship.....	40
	Relation Between Elastic Theory and Ultrasonic.....	48
	A Brief History of Ultrasonic.....	50
	Piezoelectric Transducer.....	51
	Mode of Wave Propagation in Solid.....	54
	Bulk Wave.....	54
	Surface Wave.....	55
	Lamb Wave.....	58
	Longitudinal & Shear Wave.....	58
	Longitudinal Wave Velocities.....	58
	Shear Wave Elasticity.....	59
	Summary.....	60
<b>V</b>	<b>METHODOLOGY.....</b>	<b>62</b>
	Introduction.....	62
	Glass Preparation.....	62
	Melting Process.....	62
	Casting Process.....	64
	Glass Polishing & Cutting.....	65
	Density Measurement.....	66
	Ultrasonic Measurement Techniques.....	66
	Transit Time Measurement Techniques.....	69
	Summary.....	71
<b>VI</b>	<b>ELASTIC PROPERTIES OF LEAD BORATE GLASS.....</b>	<b>74</b>
	Introduction.....	74
	Lead Borate Glass System.....	74
	Density Measurement of Lead Borate Glass.....	75
	Velocity of Wave Propagation in Lead Borate Glass.....	76
	Elastic Properties of Lead Borate Glass.....	77

CHAPTER	Page
Debye Temperatures of Lead Borate Glass.....	78
<b>VII      ULTRASONIC BEHAVIOUR OF LEAD PHOSPHATE GLASS.....</b>	<b>88</b>
Introduction.....	88
Lead Phosphate Glass System.....	88
Density of Lead Phosphate Glass.....	89
Longitudinal & Shear Wave Velocity of Lead Phosphate Glass.....	90
Elastic Properties of Lead Phosphate Glass.....	91
Debye Temperature of Lead Phosphate Glass.....	93
<b>VIII     GENERAL DISCUSSION &amp; CONCLUSION.....</b>	<b>103</b>
Discussion.....	103
Conclusion.....	109
Suggestion.....	110
<b>BIBLIOGRAPHY.....</b>	<b>112</b>
<b>VITA.....</b>	<b>115</b>
<b>APPENDICES.....</b>	<b>116</b>

## LIST OF FIGURES

Figure		Page
3.1	Basic structure of glass former.....	21
3.2	Structure of glass modifier.....	22
3.3	Structure of alkali oxide $M_2O$ is found ruptured the oxygen bonds.....	24
3.4	Structure of boroxyl groups linked by shared oxygen.....	27
3.5	Structure of $PO_4$ . Darker-shaded and open circle represent P and atom oxygen respectively.....	28
3.6	Volume-temperature diagram for glass-forming melt.....	30
4.1	Load elongation graph for glass (Bruce,1982).....	38
4.2	The stress-strain curvature.....	41
4.3	Parallelepiped using for the stress-strain relationship.....	42
4.4	Six-strain component.....	43
4.5	A diagram of shear strain defined as the change between two sides of rectangles.....	44
4.6	Six stress components.....	46
4.7	A diagram of one unit cell at normal state, (a) compressional state and (b) extension state.....	53
4.8a	The propagation of compression wave.....	55
4.8b	Shear wave propagation.....	56
4.9	Rayleigh wave.....	56
4.10a	A symmetrical Lamb wave.....	57
4.10b	A asymmetrical Lamb wave.....	57



Figure		Page
5.1	Block diagram of the MBS 8000 Measurement System..	68
5.2	A schematic diagram of sample holder.....	73
6.1	Density of lead borate glasses.....	80
6.2	Longitudinal and shear wave velocities of lead borate glasses.....	81
6.3	Elastic modulus, $C_{11}$ and $C_{44}$ of lead borate glasses.....	82
6.4	Bulk modulus of lead borate glasses.....	83
6.5	Young's modulus of lead borate glasses.....	84
6.6	Poisson ratio for lead borate glasses.....	85
6.7	Debye Temperature of lead boprate glasses.....	86
6.8	Atom per volume of lead borate glasses.....	87
7.1	Density of lead phosphate glasses.....	95
7.2	Longitudinal and shear wave velocities of lead phosphate glasses.....	96
7.3	Longitudinal modulus, $C_{11}$ and shear modulus, $C_{44}$ of lead phosphate glasses.....	97
7.4	Bulk modulus of lead phosphate glasses.....	98
7.5	A rapid decrement for Young's modulus of lead phosphate glasses.....	99
7.6	Poisson ratio for lead phosphate glasses.....	100
7.7	Variation of Debye Temperature of lead phosphate glasses.....	101
7.8	Number of atom per volume of lead phosphate glasses.....	102

## LIST OF TABLES

Table		Page
3.1	Some type of glass formers and their melting points.....	20
4.1	Elastic modulus of selected solid materials.....	38
6.1	Physical and elastic properties of lead borate glass.....	79
7.1	Physical and elastic properties of lead phosphate glass.....	94

## LIST OF SYMBOLS AND ABBREVIATIONS

SOEC	-	Second Order Elastic Constants
IR	-	infra red
NBOs	-	Nonbridging oxygens
DTA	-	Differential Thermal Analysis
EDX	-	Energy Dispersive X_ray
XRD	-	X_ray Diffraction
SEM	-	Scanning Electron Microscope
$\sigma$	-	stress
$\varepsilon$	-	strain
$e_{ij}$	-	strain components
$\sigma_{ij}$	-	stress components
$C_{rs}$	-	components of elastic constant
$\lambda, \mu$	-	Lame's constants
$V_L$	-	longitudinal velocity
$V_S$	-	shear velocity
$\nu$	-	Poisson's ratio
B	-	bulk modulus
E	-	Young's modulus
d	-	fractal dimension
$W_{air}$	-	weight of the sample in the air

$W_{\text{acetone}}$	-	weight of the sample in acetone
$\rho_s$	-	density of the glass sample
$\rho_{\text{acetone}}$	-	absolute density of acetone $\sim 0.7899 \text{ g/cm}^3$

## **CHAPTER 1**

### **INTRODUCTION**

A wide spread interest of the science and technology of glass has attracted considerable attention to scientists and researchers throughout the world. Glass is believed to have been found in the Middle East 3000 BC but it was not well developed. The development of glass has advanced a great deal in early 20th century but a rapid growth of glass technology was only started in the last sixty years. One of the earliest developments was air tempering to improve their strength.

Glass is one of man's most valuables and versatile materials in daily uses. Glass has found applications in optical data transmission, detection, sensing, laser technologies and batteries application. By glass we usually understand it as hard material, often transparent or translucent, which is made by heating together a mixture of materials such as sand, limestone and soda at a very high temperature.

#### **Glass History**

The word 'glass' is derived from an Indo European root meaning 'shiny', which has also been given the words glare, glow and glaze. Glasses and glazes were manufactured far back in human history. According to Sir W.M. Flinders Petrie, the earliest known glaze dates from

about 12000 B.C. and the earliest pure glass from about 7000 B.C. Both glasses were found in Egypt. In the West, glass manufacturing was dispersed to isolated sites after the fall of the Roman Empire but was continued in Byzantium and later in the Middle East by the Arabs.

Progress in techniques of glass manufacture and in the application of glass was subsequently rapid, in parallel with many other areas of technology. Until the twentieth century most of these advances were made empirically, using common sense to guide experimentation. The application of basic scientific understanding to the improvement of glass manufacture and to new application of glass occurred only in the last few decades. Among the first to study glass in a more basic way was Micheal Faraday (1830).

He studied the electrolysis and conductivity of various glasses. Later, Warburg and Tegetmeier (1884) found that the electrolysis of glass followed the Faraday's law. At the same time, Tammann (1884) initiated work on the viscosity of glass, glass transition, the relationship of crystallization rate and viscosity and the reasons for glass formation. Schulz (1913) made a detailed study of exchange and diffusion of silver ions for sodium ions in a commercial glass.

Joseph Fraunhopper (1787-1826) was successful in preparing the optical glass. Until the twentieth century, the Department of Glass Technology at Shelfield University, England carried out a great

experimental and theoretical approach of glass technology under Prof. W.E.S.Turner's research group. They were active in measuring such properties as density, electrical conductivity, chemical durability, viscosity and thermal expansion of a wide variety of commercial and lab glasses. Griffith proposed his hardness and brittleness theorem and Zachariasen (1935) with his Random Network Theory after the World War II. To date, glass technology application has produced various types of glass for commercial use.

### **Research Background**

Various researches had been carried out on the physical properties of the borate and phosphate glasses. The works on the elastic properties of these glasses were extremely scarced. Previously, a research done on glass was reported by the well-known Saunders and his co-workers (1990). In order to give information about the elastic properties of borate and phosphate glasses, the ultrasonic velocity and attenuation measurements have been carried out. They were found to be successful in their works. Many researchers and scientists then continued this type of work.

Since then, works on glass and its properties were burst rapidly worldwide. For example, Soga (1985) was carried out an investigation on the elastic moduli and fracture toughness of glass. Santokh and co-

workers (1989) investigated the elastic moduli of some mixed alkali borate glasses. From the measured ultrasonic velocities and densities, the elastic moduli were calculated. Senin (1994) studied the second order elastic constants of the rare earth phosphate glasses as a function of temperatures and pressure. Later, his co-worker carried out works on the elastic, inelastic and nonlinear acoustic properties of zincchloro-phosphate glass.

As mentioned previously, investigation towards the glass property is extremely scarced especially on the elastic properties of the glass. A number of works had been carried out on the physical properties of the borate and phosphate glasses. In spite of the vigorous investigation towards glass properties, to date not much work on the elastic properties of borate and phosphate glass was reported.

### **Objective of Study**

The purpose of this project is to prepare and study the elastic properties of binary lead borate  $(\text{PbO})_x(\text{B}_2\text{O}_3)_{1-x}$  and binary lead phosphate  $(\text{PbO})_x(\text{P}_2\text{O}_5)_{1-x}$  glass system as function of x mole fraction. In this work, we also studied the effect of PbO on the physical properties of both glass systems.



The present work concerns the entire range of glass that can be prepared by melting respectively, PbO and B<sub>2</sub>O<sub>3</sub> reagents and PbO and P<sub>2</sub>O<sub>5</sub> reagents in alumina crucibles. After synthesizing the glass, the ultrasonic measurements were carried out at the room temperature in order to obtain the longitudinal and shear wave velocity. Together with the density measurements, the data for elastic constant was obtained and hence the compositional dependence of the elastic moduli could be determined. Thus, knowing the strength of a glass is of practical interest, since it may determine the durability of the glass use and it may also decide the suitability of the materials for special application (Salama et.al 1994).

## Chapter Organization

In the next chapter the glass technology will be discussed including the uses of the glass and also about the glass family of interest. Then, chapter 3 describes the theory of glass, which includes the definition of glass and the explanation of the glass structures and components. The random network theory and the glass melting transition are also discussed. In chapter 4, the theory of elasticity and related elastic parameters will be described. In chapter 5, the methodology of the research is explained where the synthesizing of the glasses and the preparation of the glasses for the elastic measurements are given in detail. Chapter 6 and 7 report on the experimental results and give all the